

RESEARCH ARTICLE

Numerical simulation of composite materials with sisal and glass fibers for ballistic impact resistance

Tibebu Merde Zelelew^{1*} Addisu Negashe Ali¹ Getenet Ayele¹ Geta Kidamemariam¹ Ermias Gebrekidan Koricho²¹ Faculty of Mechanical and Industrial Engineering, Bahir Dar University, Bahir Dar, Ethiopia² Department of Mechanical Engineering, Addis Ababa Science and Technology University, Addis Ababa, Ethiopia

Correspondence to: Tibebu Merde Zelelew, Faculty of Mechanical and Industrial Engineering, Bahir Dar University, Bahir Dar, Ethiopia; Email: tibem90@gmail.com

Received: March 31, 2024;**Accepted:** June 15, 2024;**Published:** June 20, 2024.

Citation: Zelelew TM, Ali AN, Ayele G, et al. Numerical simulation of composite materials with sisal and glass fibers for ballistic impact resistance. *Mater Eng Res*, 2024, 6(1): 323-331. <https://doi.org/10.25082/MER.2024.01.003>

Copyright: © 2024 Tibebu Merde Zelelew *et al.* This is an open access article distributed under the terms of the [Creative Commons Attribution-Noncommercial 4.0 International License](https://creativecommons.org/licenses/by-nc/4.0/), which permits all noncommercial use, distribution, and reproduction in any medium, provided the original author and source are credited.



Abstract: Body armor is critical to mitigating penetrating injuries and saving soldiers' lives. However, ballistic impacts to body armor can cause back deformation (BFD), posing a serious threat of fatal injury on the battlefield. The study performs finite element modelling to evaluate the protection of body armor panels. The numerical simulations consider various parameters, including impact velocities, and angles of projectile impact, which are used to estimate the residual velocity and damage patterns of the composite laminate. The simulations are carried out using the LS-DYNA code based on finite element analysis. The main results of the research reveal crucial insights into the ballistic behavior of composite materials with sisal and glass fibers. The study identifies specific responses, damage development patterns, and comparative analyses between sisal and fiberglass composites. The results have practical implications for the development of advanced materials to improve ballistic protection.

Keywords: body armor, finite element model, fiberglass, impact velocity, sisal fiber

1 Introduction

The function of body armor is to protect by softening shock and preventing weapon penetration. However, as weapons advance, it is almost impossible to use only one type of protective gear to prevent injuries. Body armor is now manufactured in many styles and designs to fulfill its functions [1]. The composition of bulletproof materials has evolved from effortless to varying qualities and includes components such as non-Newtonian materials [2], and magnetorheological fluids [3]. The inventive development of advanced materials has significantly improved the capabilities of bulletproof equipment. Fiber-reinforced composite materials are widely used in the field of ballistic security due to their low weight, high quality, high modulus, and high specific retention energy [4]. Requests for strategies to address the ballistic response of fiber-reinforced rubber mesh composites typically include ballistic entry testing [5, 6], and limited component replicas [7–10]. Improving the ballistic infiltration resistance of advanced composite materials for ballistic security is significant because it focuses on improving the mechanical properties of high-performance strands [11, 12].

Body armor can be defensive materials used to protect different customers, including military and security forces, from various threats [13]. Today, the combination of advances in high-velocity shooting and increasing demand for body armor places critical importance on designers, forecasters, and producers. This weight arises from the need for constant development of ballistic security systems, which requires not only appropriate planning strategies but also the further development of suitable materials [14].

Due to variations in the angle of incidence of the impacting projectile, a composite structure may be exposed to the ballistic impact force at different points in its life. This is an important equipment. It is important to ensure that laminated structural composites are resistant to penetration and perforation from projectile impacts of different orientations. The transverse normal impact-induced perforation in composite panels has been numerically analyzed in previous publications [15–17]. These studies considered variables such as shot tip shape, stack grouping, and target thickness and provided experience on their effects on target aperture. By combining glass and sisal fibers, a hybrid material can be created that benefits from the strengths of both fibers. Glass fibers provide high thermal stability and corrosion resistance, while sisal fibers reinforce the glass and improve its strength and ductility. This hybridization can result in

a material with improved ballistic performance and impact resistance, making it suitable for use in protective applications [18, 19]. The combination of biodegradable and renewable sisal fibers with synthetic and durable glass fibers also provides environmental benefits by using a sustainable and renewable resource [20]. Overall, the hybridization of glass and sisal fibers offers a promising solution to improve the performance and sustainability of materials used in protective applications [21, 22].

The importance of ballistic performance and impact resistance is critical in various applications including military, law enforcement, and civilian scenarios. It is essential to protecting lives and resources. Developing materials and structures that can effectively resist and mitigate ballistic threats is of paramount importance. In addition, the impact resistance of materials is critical to ensuring the durability and reliability of structures and systems subjected to dynamic forces. Research and development efforts focus on achieving optimal ballistic performance and impact resistance in a wide range of applications and address the evolving safety requirements of various sectors [23–25].

Ballistic impact is the study that deals with the behavior of material failure caused by the impact of projectiles/bullets. This is particularly important to protect people and machines in nuclear and military applications. The impact behavior of composite materials depends on the size, shape, mass, impact velocity, and material of the projectile [26, 27], as well as the geometry, mass, composition, and contact condition of the target [28]. For the ballistic investigation of composite materials, numerical analysis using finite element analysis (FEA) is also investigated [29, 30]. Through validation, it was found that FEA methods can predict behavior quite realistically [31–33].

The purpose of this study is to investigate the perforation behavior of glass and sisal fiber composite panels when exposed to blunt projectiles from different angles and velocities. The study aims to analyze the influence of impact angle (45° and 90°) and impact velocity in the range of 100-200m/s on the perforation properties of the target plate through numerical simulation using LSDYNA.

2 Numerical simulation

2.1 Finite element modelling

The target plate considered for investigation is a square plate of exposed area dimension of $100\text{ mm} \times 100\text{ mm} \times 10\text{ mm}$ having 20 layers of bullet fabric (glass, and sisal). Each layer of the target is modelled using Belytchko-Tsay shell elements with a layer thickness of 0.5 mm. To arrive at the optimum finite element, a detailed mesh convergence study with different element sizes is carried out. As per the investigation, 2 mm element sizes are converging to the same residual velocity. Hence for computational efficiency, a 2 mm element size is used for subsequent studies. The finite element model of the target plate consists of 340,000 elements and 344,008 nodes. The projectile is modelled using the three-dimensional solid elements available in the LSDYNA code. The hemispherical nose projectile model is made up of 3950 elements and 4344 nodes. The finite element model of the target plate and the projectile is shown in Figure 1. In modelling the projectile, the shank diameter of 9 mm is kept constant for the hemispherical-nosed projectile, and the length of 19 mm for the hemispherical-nosed projectile is considered to maintain the 8 g of projectile mass.

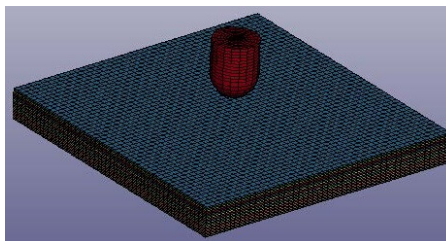


Figure 1 Finite element modelling

2.2 Material model

To simulate the ballistic impact effects on Sisal and glass fiber plate numerically, MAT 54 Enhanced composite damage material-based Chang – Chang failure criteria, available in the non-linear finite element code LS DYNA is used [42]. For composite backing panels, the

MAT_ENHANCED_COMPOSITE_DAMGE model(MAT54) was used and the Chang/Change criteria are given as follows [43]:

$$e_f^e = \left(\frac{\sigma_{aa}}{X_t}\right)^2 + \beta \left(\frac{\sigma_{ab}}{S_c}\right) - 1 \begin{cases} \geq 0 & \text{failed} \\ < 0 & \text{elastic} \end{cases} \tag{1}$$

$$E_a = E_b = G_{ab} = \nu_{ba} = \nu_{ab} = 0 \tag{2}$$

For the compressive fiber mode, $\sigma_{aa} < 0$:

$$e_c^2 = \left(\frac{\sigma_{aa}}{X_c}\right)^2 - 1 \begin{cases} \geq 0 & \text{failed} \\ < 0 & \text{elastic} \end{cases} \tag{3}$$

$$E_a = \nu_{ba} = \nu_{ab} = 0 \tag{4}$$

For the tensile matrix mode, $\sigma_{bb} > 0$:

$$e_m^2 = \left(\frac{\sigma_{bb}}{Y_t}\right)^2 + \left(\frac{\sigma_{ab}}{S_c}\right)^2 - 1 \begin{cases} \geq 0 & \text{failed} \\ < 0 & \text{elastic} \end{cases} \tag{5}$$

$$E_b = \nu_{ab} = 0 \Rightarrow G_{ab} = 0 \tag{6}$$

For the compressive matrix mode, $\sigma_{bb} < 0$:

$$e_d^2 = \left(\frac{\sigma_{bb}}{2S_c}\right)^2 + \left[\left(\frac{Y_c}{2S_c}\right)^2 - 1\right] \left(\frac{\sigma_{bb}}{S_c}\right) + \left(\frac{\sigma_{ab}}{S_c}\right)^2 - 1 \begin{cases} \geq 0 & \text{failed} \\ < 0 & \text{elastic} \end{cases} \tag{7}$$

$$E_a = \nu_{ba} = \nu_{ab} = 0 \Rightarrow G_{ab} = 0 \tag{8}$$

Where is the stress in the fiber direction, σ_{bb} is the stress in the matrix direction, G_{ab} is the inplane shear stress, X_t is the longitudinal tensile strength, X_c is the longitudinal compressive strength, Y_t is the transverse tensile strength, Y_c is the transverse compressive strength, S_c is the shear strength, β is the weighting factor for the shear term in tensile fiber mode. The material properties used in the numerical simulation are given in Table 1 and 2.

Table 1 Mechanical properties of sisal and glass fiber [39, 40]

Properties	Sisal	E-Glass
Density (g/cm ³)	1.5	2.5
Longitudinal Elastic Modulus: E ₁ (GPa)	28	53.48
Transverse Elastic Modulus: E ₂ (GPa)	2.5	17.7
Radial Elastic Modulus: E ₃ (GPa)	2.5	5.83
Shear Modulus: G ₁₂ (GPa)	1.85	5.83
Poisson's Ratio: ν_{12}	0.265	0.278
Tensile Strength: X _t (MPa)	600	1140
Compressive Strength: X _c (MPa)	450	570
Tensile Yield Strength: Y _t (MPa)	30	35
Compressive Yield Strength: Y _c (Mpa)	100	114
Shear Strength: S _c (MPa)	60	72

Table 2 Material properties of steel projectiles [41]

Properties	Steel
Density [kg/m ³]	7830
E ₁ (GPa)	210
ν	0.3

3 Impact conditions

To understand how composite panels respond to different ballistic scenarios, it is crucial to incorporate various impact parameters into the simulation. These parameters include impact velocity and angles. The behavior of composite panels based on glass fiber woven fabrics and a bi-component epoxy resin under ballistic impacts was evaluated using a finite-element model at the meso scale [20] while considering parameters such as projectile material, size,

and speed [44]. The development of a comprehensive framework for the design of composite structures at different levels requires accurate mathematical and computational models that can simulate the dynamic impact on composite panels [45]. Numerical studies have been conducted to investigate the damage effects on composite panel high-velocity impacts, considering different composite laminates and stacking sequences [46, 47]. These studies provide insights into the ballistic behavior, energy-absorbing capacity, and damage of composite panels' performance under different impact scenarios.

4 Energy absorption

The assessment of energy absorption is a critical aspect in the numerical simulation of composites with sisal and glass fibers for ballistic impact resistance. The simulation involves modelling and analyzing how the composite materials absorb and dissipate energy when exposed to ballistic impacts. Several studies have investigated the impact resistance and ballistic performance of different composite materials. The results have shown that the difference in velocity and angle significantly affects the energy absorption capacity of the composites [48, 49]. Additionally, the orientation of the fibers in the impact direction has been found to improve the impact energy absorption and overall mechanical response of the composites [50, 51]. Finite element simulations have been used to evaluate the behavior of composite panels under ballistic impacts, providing insights into the number of layers broken, delamination effects, and deformation patterns [20].

5 Result and discussion

Understanding the failure mechanisms in numerical simulations of composites for ballistic impact resistance is crucial for assessing their performance under extreme conditions. Different failure mechanisms can occur depending on factors such as impact velocity, angle, and the properties of the composite. The failure mechanisms that may be investigated in such simulations include the energy absorption/dissipation capabilities and failure mechanisms of hyper-elastic target materials [52, 53]. The impact of the target surface will be affected by different velocity ranges and angles observed in the simulation. The numerical simulation using the same thickness of the target sample was made. The numerical simulation results are to indicate the effect of the parameters and identify better materials and control parameters. In Figure 2(a), the illustration shows that the kinetic energy absorption of the composite panels varies. Glass fiber exhibits superior ballistic impact resistance, withstanding velocities of 120 m/s at a 90-degree angle better than sisal fiber in terms of energy absorption and dissipation. Figure 2(b) demonstrates that sisal fiber target panels are easily penetrated by bullets due to their lower strength compared to glass fiber. Figure 3(a) indicates that the residual velocity of sisal fiber is lower because it easily damages the target panel, whereas glass fiber maintains a higher residual velocity due to its rigidity. This difference in material properties highlights glass fiber's superiority over sisal fiber. Figure 3(b) further emphasizes that residual velocities are influenced by both the angle of projection and material properties.

Figure 4 and 5 describe the Von Mises stress effect on the composite panel when impacted by bullets at different angles and velocities, resulting in distinct damage patterns. The higher damage to the fibers occurs when the projectile tip contacts the panels and spreads perpendicular to the loading direction. The strength of the fibers in their respective layers significantly influences the overall strength of the panels [26, 54]. Upon impact with a 9 mm FMJ (Full Metal Jacket) projectile, the fully damaged shear area on the impact side is smaller compared to the backside across all panels.

Figure 6 illustrates the comparison between sisal and glass fiber regarding their ballistic impact resistance behavior and stress resistance in composite materials. According to finite element analysis, sisal fiber exhibits greater rigidity properties compared to glass fiber, as it tends to break more easily without stretching. When impacted at a velocity of 150 m/s at a 90-degree angle, sisal fiber experiences a higher damage pattern. On the other hand, glass fiber outperforms sisal fiber in terms of ballistic impact resistance and higher energy absorption capabilities.

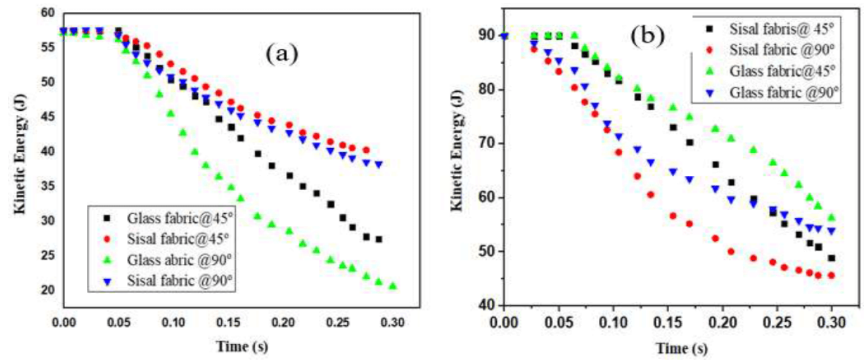


Figure 2 Illustrates kinetic energy vs time (a) for glass &sisal fabric @ velocity of 120m/s with different angles, and (b) for glass &sisal fabric @ a velocity of 150m/s with a different angles

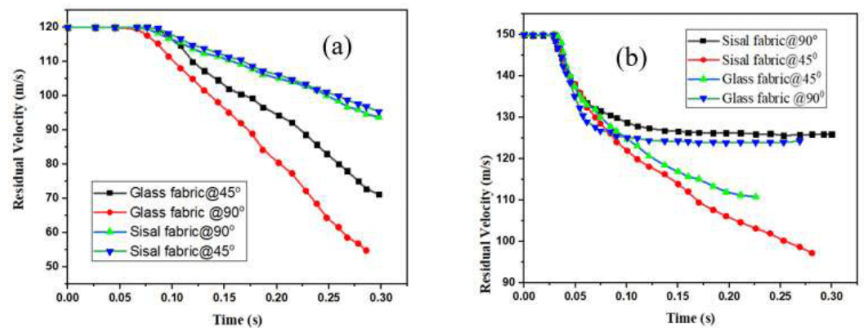


Figure 3 Illustrates Residual velocity vs time (a) for glass &sisal fabric @the of the velocity of 120m/s with a different angle, and (b) for glass &sisal fabric @the of the velocity of 150m/s with a different angle

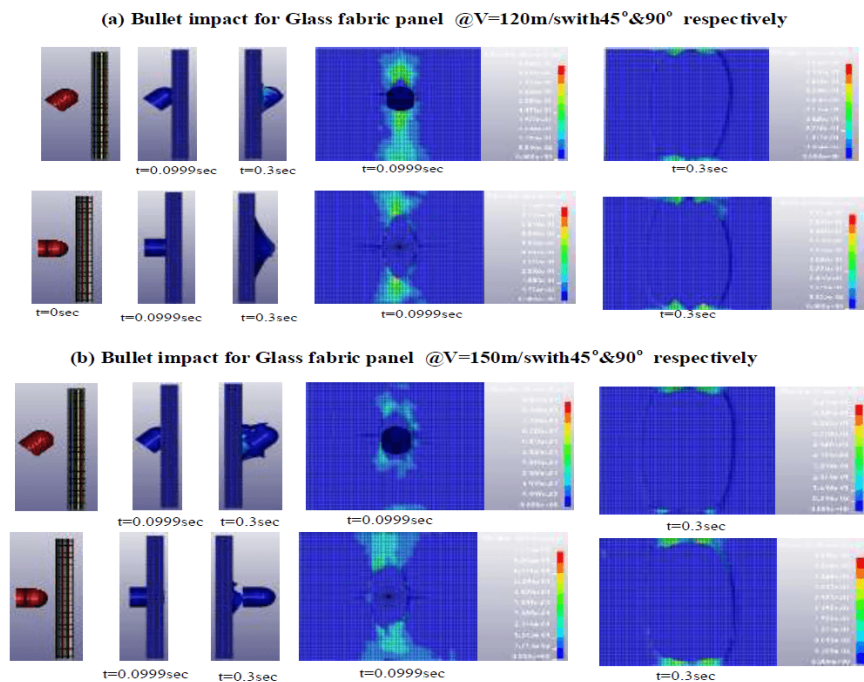


Figure 4 V.Mises stress of bullet impact for Glass fabric panel @ velocity of 120 m/s & 150 m/s with 45° & 90° respectively

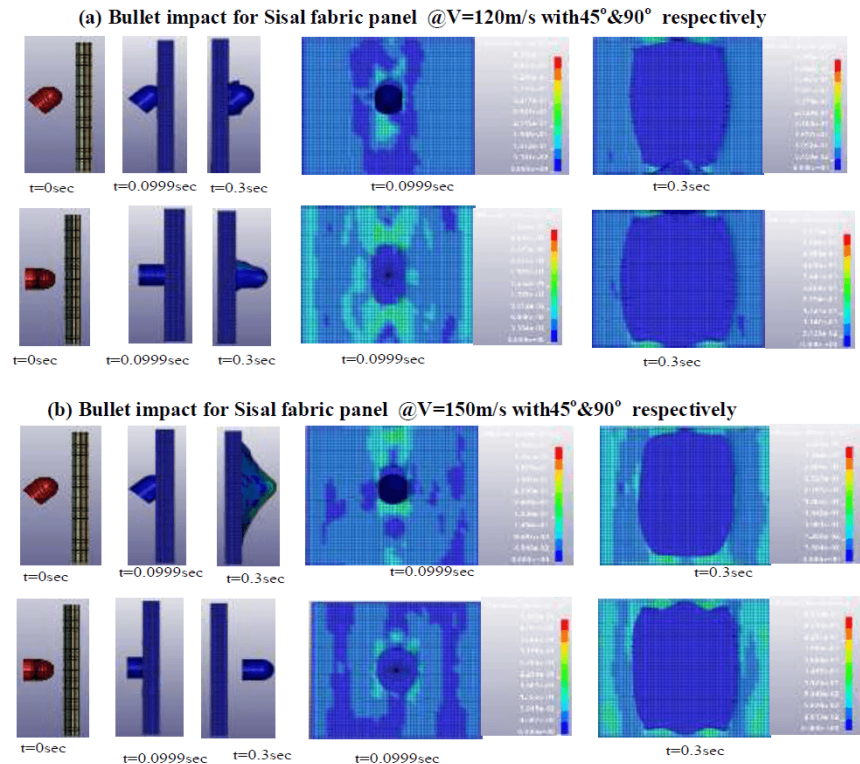


Figure 5 V.Mises stress of bullet impact for sisal fabric panel @ velocity of 120 m/s & 150 m/s with 45° & 90° respectively

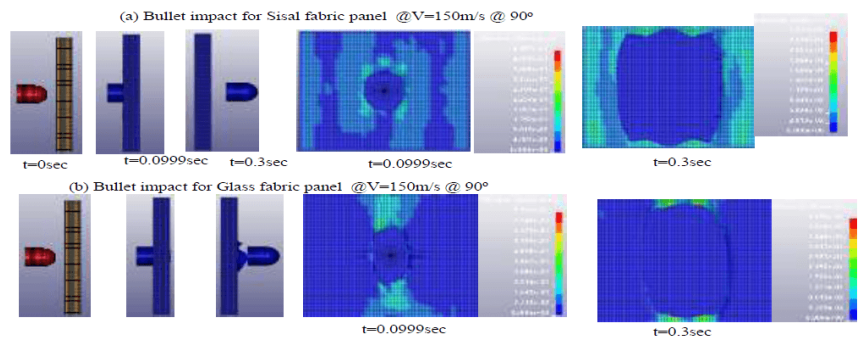


Figure 6 V.Mises stress of bullet impact for Sisal fabric and glass fabric @ velocity of 150 m/s with 90°

6 Conclusion

The finite element modelling of the glass and sisal fiber composite panels is developed and simulated by considering various parameters. Damage initiation and damage propagation-based failure are developed. The glass fiber panel demonstrated better performance than sisal fiber with a ballistic limit velocity of 150 m/s, whereas sisal fiber performed worse with a ballistic impact of 120 m/s. due to glass fiber grater damage dissipation energy and higher extension of fiber tension than sisal fiber lamina, glass fiber as their backing layer showed excellent resistance to ballistic impact with a velocity of 120 m/s. natural fiber is particularly biodegradable and significantly reduces the overall cost compared to glass fiber with approximately the same performance.

Conflicts of interest

The authors declare that they have no conflict of interest.

References

- [1] Badea SM, Lăzăroaie C, Zecheru T, et al. Methods And Criteria For Selecting The Suitable Materials To Achieve The New Ballistic Protection Vest Designed To Womens. International conference KNOWLEDGE-BASED ORGANIZATION. 2015, 21(3): 782-786.
<https://doi.org/10.1515/kbo-2015-0132>
- [2] Pacek D, Zochowski P, Wisniewski A. Anti-trauma pads based on non-Newtonian materials for flexible bulletproof inserts[C]//Proceedings of the 29th International Symposium on Ballistics, Scotland, UK. 2016: 9-13.
- [3] Wiśniewski A, Pacek D, Zochowski P, et al. Optimization of the material systems with magnetorheological fluids. Proceedings-28th International Symposium on Ballistics, BALLISTICS 2014.
- [4] Crouch IG. Body armour – New materials, new systems. Defence Technology. 2019, 15(3): 241-253.
<https://doi.org/10.1016/j.dt.2019.02.002>
- [5] Ansari MdM, Chakrabarti A. Ballistic Performance of Unidirectional Glass Fiber Laminated Composite Plate under Normal and Oblique Impact. Procedia Engineering. 2017, 173: 161-168.
<https://doi.org/10.1016/j.proeng.2016.12.053>
- [6] Meyer CS, Haque BZ (Gama), O'Brien DJ, et al. Mesoscale ballistic damage mechanisms of a single-layer woven glass/epoxy composite. International Journal of Impact Engineering. 2018, 113: 118-131.
<https://doi.org/10.1016/j.ijimpeng.2017.11.005>
- [7] Nguyen LH, Lässig TR, Ryan S, et al. A methodology for hydrocode analysis of ultra-high molecular weight polyethylene composite under ballistic impact. Composites Part A: Applied Science and Manufacturing. 2016, 84: 224-235.
<https://doi.org/10.1016/j.compositesa.2016.01.014>
- [8] Abteu MA, Boussu F, Bruniaux P, et al. Ballistic impact performance and surface failure mechanisms of two-dimensional and three-dimensional woven p-aramid multi-layer fabrics for lightweight women ballistic vest applications. Journal of Industrial Textiles. 2019, 50(9): 1351-1383.
<https://doi.org/10.1177/1528083719862883>
- [9] Dewangan MK, Panigrahi S. Finite element analysis of projectile nose shapes in ballistic perforation of 2D plain woven Kevlar/epoxy composites using multi-scale modelling. Journal of Industrial Textiles. 2020, 51(3_suppl): 4200S-4230S.
<https://doi.org/10.1177/1528083720970168>
- [10] Nguyen LH, Ryan S, Orifici AC, et al. A penetration model for semi-infinite composite targets. International Journal of Impact Engineering. 2020, 137: 103438.
<https://doi.org/10.1016/j.ijimpeng.2019.103438>
- [11] Staniszewski JM, Bogetti TA, Wu V, et al. Interfibrillar behavior in ultra-high molecular weight polyethylene (UHMWPE) single fibers subjected to tension. International Journal of Solids and Structures. 2020, 206: 354-369.
<https://doi.org/10.1016/j.ijsolstr.2020.09.021>
- [12] Lee J, Kim SS, Kang D, et al. Physicochemical characterization of polyimide (PI) / paramid: New functional and safe materials with improved heat resistance by a simple coating of polyimide on the surface of p-aramid. Progress in Organic Coatings. 2019, 127: 117-123.
<https://doi.org/10.1016/j.porgcoat.2018.11.012>
- [13] El Messiry M, El-Tarfawy S. Performance of weave structure multi-layer bulletproof flexible armor. Proceedings of the 3rd Conference of the National Campaign for Textile Industries, NRC Cairo, "Recent Manufacturing Technologies and Human and Administrative Development", Cairo, Egypt. 2015: 9-10.
- [14] Othman AR, Hassan MH. Effect of different construction designs of aramid fabric on the ballistic performances. Materials & Design. 2013, 44: 407-413.
<https://doi.org/10.1016/j.matdes.2012.07.061>
- [15] Tran P, Ngo TD, Ghazlan A. Numerical modelling of hybrid elastomeric composite panels subjected to blast loadings. Composite Structures. 2016, 153: 108-122.
<https://doi.org/10.1016/j.compstruct.2016.05.103>
- [16] Gama BA, Gillespie JW. Finite element modeling of impact, damage evolution and penetration of thick-section composites. International Journal of Impact Engineering. 2011, 38(4): 181-197.
<https://doi.org/10.1016/j.ijimpeng.2010.11.001>
- [17] Ansari MM, Chakrabarti A. Behaviour of GFRP composite plate under ballistic impact: experimental and FE analyses. Structural Engineering and Mechanics. 2016, 60(5): 829-849.
<https://doi.org/10.12989/sem.2016.60.5.829>
- [18] Abdurohman K, Adhitya M, Nugroho A. Durability Study of Glass/Carbon Hybrid Composites Immersed in Seawater for Marine Application. Key Engineering Materials. 2023, 941: 241-247.
<https://doi.org/10.4028/p-7titb8>
- [19] Asmare S, Yoseph B, Jamir TM. Investigating the impact resistance of E-glass/ Polyester composite materials in variable fiber-to-matrix weight ratio composition. Cogent Engineering. 2023, 10(1).
<https://doi.org/10.1080/23311916.2023.2178110>
- [20] Ojoc GG, Chiper Titire L, Muntea C, et al. Ballistic Response of a Glass Fiber Composite for Two Levels of Threat. Polymers. 2023, 15(4): 1039.
<https://doi.org/10.3390/polym15041039>

- [21] Suhaimi AA, Ali A, et al. Impact Behaviour of Laminated Bamboo, E-Glass and Hybrid Bamboo/E-Glass Fibre Composites. *International Journal of Integrated Engineering*. 2022, 14(8). <https://doi.org/10.30880/ijie.2022.14.08.012>
- [22] Pathak RK, Patel S, Gupta VK. A novel design of hybrid ceramic composite plate under ballistic impact. *Mechanics of Advanced Materials and Structures*. 2022, 30(24): 5015-5033. <https://doi.org/10.1080/15376494.2022.2111623>
- [23] Xu H, Wang X, Wang B, et al. Study of the Influence Factors for Ballistic Performance of Glass Fiber Reinforced Composites. *Journal of Physics: Conference Series*. 2023, 2460(1): 012096. <https://doi.org/10.1088/1742-6596/2460/1/012096>
- [24] Safaat A, Sutikno. Ballistic Performance of Epoxy-Ramie Composite - SiC Layered Body Armor Using Finite Element Analysis. *Key Engineering Materials*. 2023, 941: 271-277. <https://doi.org/10.4028/p-5755oc>
- [25] Purwanto H, Tauviqirrahman M, Sugiarto S, et al. Analysis projectile performance in ballistic tests using compressed air gun. *EUREKA: Physics and Engineering*. 2022, 6: 120-127.
- [26] Naik NK, Shirao P, Reddy BCK. Ballistic impact behaviour of woven fabric composites: Parametric studies. *Materials Science and Engineering: A*. 2005, 412(1-2): 104-116. <https://doi.org/10.1016/j.msea.2005.08.019>
- [27] Tan VBC, Lim CT, Cheong CH. Perforation of high-strength fabric by projectiles of different geometry. *International Journal of Impact Engineering*. 2003, 28(2): 207-222. [https://doi.org/10.1016/s0734-743x\(02\)00055-6](https://doi.org/10.1016/s0734-743x(02)00055-6)
- [28] Børvik T, Hopperstad OS, Berstad T, et al. Perforation of 12mm thick steel plates by 20mm diameter projectiles with flat, hemispherical and conical noses. *International Journal of Impact Engineering*. 2002, 27(1): 37-64. [https://doi.org/10.1016/s0734-743x\(01\)00035-5](https://doi.org/10.1016/s0734-743x(01)00035-5)
- [29] Sikarwar RS, Velmurugan R. Ballistic Impact on Glass/Epoxy Composite Laminates. *Defence Science Journal*. 2014, 64(4): 393-399. <https://doi.org/10.14429/dsj.64.3882>
- [30] Goo JS, Kim JS, Shin KB. Evaluation of structural integrity after ballast-flying impact damage of a GFRP lightweight bogie frame for railway vehicles. *Journal of Mechanical Science and Technology*. 2015, 29(6): 2349-2356. <https://doi.org/10.1007/s12206-015-0528-9>
- [31] Ramadhan AA, Abu Talib AR, Mohd Rafie AS, et al. High velocity impact response of Kevlar-29/epoxy and 6061-T6 aluminum laminated panels. *Materials & Design*. 2013, 43: 307-321. <https://doi.org/10.1016/j.matdes.2012.06.034>
- [32] Iqbal MA, Diwakar A, Rajput A, et al. Influence of projectile shape and incidence angle on the ballistic limit and failure mechanism of thick steel plates. *Theoretical and Applied Fracture Mechanics*. 2012, 62: 40-53. <https://doi.org/10.1016/j.tafmec.2013.01.005>
- [33] Anish, Gupta KK, Kumar A, et al. Dynamic response with mass variation of laminated composite twisted plates. *Journal of Mechanical Science and Technology*. 2018, 32(9): 4145-4152. <https://doi.org/10.1007/s12206-018-0812-6>
- [34] Ngaga H, Haule L, Nambela L. Review on Modifications of Sisal Fibers for Textile Applications. *Tanzania Journal of Engineering and Technology*. 2023, 42(2): 250-265. <https://doi.org/10.52339/tjet.v42i2.916>
- [35] Okpe PC, Folorunso O. Investigating the mechanical properties of sisal/coconut palm hybrid fiber reinforced epoxy composite. *Materialwissenschaft und Werkstofftechnik*. 2023, 54(5): 637-645. <https://doi.org/10.1002/mawe.202200211>
- [36] Yimer T, Gebre A. Effect of Fiber Treatments on the Mechanical Properties of Sisal Fiber-Reinforced Concrete Composites. Mo KH, ed. *Advances in Civil Engineering*. 2023, 2023: 1-15. <https://doi.org/10.1155/2023/2293857>
- [37] Guo Y, Xiang K, Wang H, et al. Experimental study on self-healing and mechanical properties of sisal fiber-loaded microbial concrete. *Materials Research Express*. 2023, 10(4): 045701. <https://doi.org/10.1088/2053-1591/acc718>
- [38] Gurusamy P, Sundeep S, Karthick SSG, et al. Mechanical Properties of Hybrid Composites on Epoxy Resin with Sisal Fiber, Carbon Fiber and Silicon Carbide. *International Journal of Vehicle Structures and Systems*. 2023, 15(2). <https://doi.org/10.4273/ijvss.15.2.14>
- [39] Bresciani LM, Manes A, Ruggiero A, et al. Experimental tests and numerical modelling of ballistic impacts against Kevlar 29 plain-woven fabrics with an epoxy matrix: Macro-homogeneous and Meso-heterogeneous approaches. *Composites Part B: Engineering*. 2016, 88: 114-130. <https://doi.org/10.1016/j.compositesb.2015.10.039>
- [40] Soden PD, Hinton MJ, Kaddour AS. Lamina properties, lay-up configurations and loading conditions for a range of fibre reinforced composite laminates. *Failure Criteria in Fibre-Reinforced-Polymer Composites*. Published online 2004: 30-51. <https://doi.org/10.1016/b978-008044475-8/50003-2>
- [41] Karthick P, Ramajeyathilagam K. Numerical study of influence of target thickness and projectile incidence angle on ballistic resistance of the GFRP composites. *Materials Today: Proceedings*. 2021, 47: 992-999. <https://doi.org/10.1016/j.matpr.2021.05.459>

- [42] Hallquist JO. LS-DYNA keyword user's manual. Livermore Software Technology Corporation. 2007, 970: 299-800.
- [43] Dong G, Li X, Ji Y. An experimental and numerical study on the ballistic performance of a lightweight ceramic composite armor. *Journal of Physics: Conference Series*. 2023, 2478(7): 072030. <https://doi.org/10.1088/1742-6596/2478/7/072030>
- [44] Palani S, Karthik S, Rajaravi C, et al. Analysis of Impact Strength on Polymer Matrix Composites Using Projectile Parameters for Combat Vehicle Application. *Lecture Notes in Mechanical Engineering*. Published online September 29, 2022: 271-281. https://doi.org/10.1007/978-981-19-3053-9_22
- [45] Shyamsunder L, Maurya A, Rajan SD, et al. Impact simulation of composite panels for aerospace applications. *Composites Part B: Engineering*. 2022, 247: 110320. <https://doi.org/10.1016/j.compositesb.2022.110320>
- [46] Pathak RK, Patel S, Gupta VK. Ballistic Impact Behavior of 3D Hybrid Composite Laminates. *Recent Advances in Machines and Mechanisms*. Published online October 4, 2022: 715-724. https://doi.org/10.1007/978-981-19-3716-3_58
- [47] Pathak RK, Patel S, Gupta VK. Ballistic Performance of 3D Hybrid Composite Laminates. *Advances in Manufacturing Technology and Management*. Published online November 11, 2022: 115-123. https://doi.org/10.1007/978-981-16-9523-0_13
- [48] Boljen M, Jenerowicz M, Bauer S, et al. Combining protective clothes with human body models for finite element ballistic impact simulations. *Communications in Development and Assembling of Textile Products*. 2023, 4(2): 141-150. <https://doi.org/10.25367/cdatp.2023.4.p141-150>
- [49] Ramagiri B, Yerramalli CS. Numerical investigation on the role of out-of-plane fiber direction on impact resistance of composite target. *Journal of Reinforced Plastics and Composites*. 2023, 43(3-4): 169-182. <https://doi.org/10.1177/07316844231158176>
- [50] Bezerra WBA, Lazarus BS, Costa UO, et al. Energy Absorption and Ballistic Performance of Epoxy Composite Reinforced with Arapaima Scales. *Polymers*. 2023, 15(7): 1614. <https://doi.org/10.3390/polym15071614>
- [51] Alimirzaei S, Ahmadi Najafabadi M, Nikbakht A, et al. Investigation of energy absorption capacity of 3D filament wound composite tubes: experimental evaluation, numerical simulation, and acoustic emission monitoring. *Mechanics of Advanced Materials and Structures*. 2023, 31(13): 2727-2742. <https://doi.org/10.1080/15376494.2022.2163437>
- [52] Zochowski P, Cegła M, Szczurowski K, et al. Experimental and numerical study on failure mechanisms of the 7.62×25 mm FMJ projectile and hyperelastic target material during ballistic impact. *Continuum Mechanics and Thermodynamics*. 2023, 35(4): 1745-1767. <https://doi.org/10.1007/s00161-023-01210-2>
- [53] Żochowski P, Cegła M, Berent J, et al. Experimental and numerical study on failure mechanisms of bone simulants subjected to projectile impact. *International Journal for Numerical Methods in Biomedical Engineering*. 2023, 39(4). <https://doi.org/10.1002/cnm.3687>
- [54] Pham QH, Long CT, Kanit T, et al. Mechanical performance and failure analysis of a fabric subjected to ballistic impact using multi-scale numerical modelling. *Journal of Composite Materials*. 2023, 57(7): 1331-1342. <https://doi.org/10.1177/00219983231153956>